



Crystal structure changes and weight kinetics of silicon-hexaboride under gamma irradiation dose

M.N. Mirzayev^{a,b,*}, S.H. Jabarov^{a,c}, E.B. Asgerov^a, R.N. Mehdiyeva^b, T.T. Thabethe^d, S. Biira^e, N.V. Tiep^a

^a Joint Institute for Nuclear Research, 141980 Dubna, Russia

^b Institute of Radiation Problems, ANAS, AZ 1143 Baku, Azerbaijan

^c Institute of Physics, ANAS, AZ 1143 Baku, Azerbaijan

^d Department of Physics, University of Pretoria, Pretoria 0002, South Africa

^e Department of Physics, Busitema University, P.O. Box 236, Tororo, Uganda



ABSTRACT

The silicide hexaboride (B_6Si) was irradiated with ^{60}Co at room temperature to study the structural changes and weight kinetics. The B_6Si samples were irradiated using a gamma source with a dose rate (D) of 0.27 Gy/s. At adsorption dose range of 9.7, 48.5, 97, 145.5 and 194 kGy. The samples were analysed using X-ray diffraction (XRD) and Energy dispersive spectroscopy (EDS) to study the microstructural and composition changes. The XRD results showed the crystalline structure for the sample before and after irradiation (with gamma irradiation dose 9.7, 48.5 and 97 kGy). Amorphization of the sample began at the gamma irradiation dose of 145.5 kGy. Increase in gamma irradiation dose had an inverse effect on the activation energy and had a directly proportional effect on the lattice volume.

Introduction

Different boron compounds such as BSi_n , B_nC , $SiBC$, $BC-ZrC$ and $BSi-ZrC$ are used in nuclear technology. The use of boron compounds is due to their exceptional physical and chemical properties when compared with other compounds [12,1]. Furthermore, B-Si composites are used in the production of photoelectric converters in electronic systems [10,21]. Current studies are focusing on the investigating the physical and mechanical properties of B_6Si compounds for use in nanotechnology application [18]. These studies focused on high thermodynamic parameters [9,24], 20 GPa pressure resistance of B-Si binary system and little friction coefficient of the ceramic systems which are used to create B_6Si compound with metal oxides in the aquatic environment [25]. Researches have shown that B_6Si lacks wear resistance in various environments, thus have spark great interest in studying the B_6Si combination [14]. Studies have also intensively investigated “self-healing components” [22] properties of B_6Si components [11,19,17]. The study of the crystal structure of B_6Si compound by X-ray diffraction method in a number of scientific researchers showed that, $P6mm$ has an orthomorph symmetry of the spatial group. Lattice parameter values of: $a = 14.397(7)$, $b = 18.318(9)$, $c = 9.911(7)$ Å and, determined which electron density appears to contain 43 silicon atoms and 238 boron atoms [20]. It is known that changing the structure parameters will also change the physical properties [25,3]. There are two major causes for the structural degradation

of silicide hexaboride compound namely: Oxidation with influence of temperature and amorphous process with gamma irradiation [26,4,5]. Under the influence of the temperature, the information about the mechanism of oxidation in the B_6Si compound is given [13,2]. However, under the influence of gamma radiation, the mechanism of the process is different from that occurring under the influence of the temperature. The created active centres are subjected to non-covalent with oxygen and carbon atoms, which is up to the temperature of 1200 K. The gamma irradiated samples create active centres and defects in the B_6Si structure. In both processes, the value of the temperature factor is required for the breakdown of bonds between the B-Si atoms and the dose boundary value of the radiation. The initial value for the activation of the active B and Si bond with the effect of the temperature is 810 K. Most studies focused on the structural properties of the silicide hexaboride (B_6Si) compound with the effect of the temperature, but the effect of radiation on the crystal structure of B_6Si compound has not been studied sufficiently. This study focused on the effect of irradiation of B_6Si and determining the energy state of the system before and after irradiation.

Materials and methods

Silicide hexaboride (B_6Si) compound with a density of 2.43 g/cm^3 and a purity of 99.5% (US Research Nanomaterials, Inc., TX, USA, Table 1) was used.

* Corresponding author at: Joint Institute for Nuclear Research, 141980 Dubna, Russia.
E-mail address: matlab@jinr.ru (M.N. Mirzayev).

<https://doi.org/10.1016/j.rinp.2018.06.034>

Received 23 April 2018; Received in revised form 11 June 2018; Accepted 14 June 2018

Available online 21 June 2018

2211-3797/ © 2018 Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Table 1
Chemical Composition (wt%).

Atom	B	Si	O	Al	Ni	Fe	C
wt, %	60	39	< 0.2	< 0.1	< 0.05	< 0.02	< 0.01

The sample was irradiated with ^{60}Co source with energy of 1.17 MeV at a K-25 radiation-chemical facility, (High Technologies Centres, Azerbaijan National Academy of Sciences) by gamma rays at dose rate $D = 0.27 \text{ Gy/s}$ at different adsorbed doses of 9.7, 48.5, 97, 145.5 and 194 kGy. The phase analysis was performed using D8 ADVANCE X-ray diffractometer (XRD) with $\text{Cu K}\alpha$ radiation ($\lambda = 1.5406 \text{ \AA}$), at operating voltage and current of 40 kV and 40 mA respectively. In order to carry out X-ray diffraction studies, powder samples were prepared from the B_6Si crystal samples. Scanning Electron Microscope, ZEISS, SIGMA VP) EDS component was used to perform the surface morphology and microcircular analysis. The analysis was measured at the 300 K standard room temperature. The error of determination did not exceed 1% at 300 K. The electron source of SEM was zirconium tungsten ring. For processing thermo emotion, the given resistance range from 100 V to 30 keV was used. The distance of electronic source to sample was $\leq 10 \text{ mm}$. The experiment was performed under vacuum condition of 10^{-7} Pa generated by turbo-molecular pumps. With the SE2 detector energy was used to investigated particle size and microstructure. Thermal studies were carried out using the Perkin Elmer, Simultaneous Thermal Analyser, STA 6000. The effect of the temperature on the kinetics processes taking place in the sample have been studied by the experimental thermal analysis. In the thermal analysis, the sample was heated from 300 K to 850 K at a heating rate of 5 K/min and at Ar gas flow rate of 20 ml/min. After heating the sample for 110 min, it was then cooled in the PolyScience analyser cooling system.

Results and discussion

The B_6Si samples were gamma irradiated with different absorption doses at room temperature and the XRD pattern for the samples before and after irradiation is shown in Fig. 1. The unirradiated B_6Si XRD pattern indicated the structure of the sample to be crystalline. The lattice parameters values for the unirradiated sample were: $a = 14.0605(5) \text{ \AA}$, $b = 18.0279(2) \text{ \AA}$ and $c = 9.2692(7) \text{ \AA}$. The results showed that under atmospheric pressure and room temperature, the B_6Si has an orthomorph symmetry and crystalline structure of $Pn\bar{m}$ spatial group. Our results were in agreement with results from previous studies [20,8]. A change in the peak intensity on the XRD pattern for the samples which were gamma irradiated with an adsorption dose range of $0 \leq D \leq 97 \text{ kGy}$ was observed. The B_6Si peak intensities were seen to fluctuations with increase in irradiation fluence from $0 \leq D \leq 97 \text{ kGy}$. This change in the peak intensity can be explained to be due to the crystal structural changes of the samples. That is, crystals (atoms) rearrange themselves during irradiation process causing a change in the crystal structure of the material. However, the silicide hexaboride compound keeps its $Pn\bar{m}$ orthogonal structure. When the gamma adsorption dose was increased to $D \geq 145.5 \text{ kGy}$, it resulted into a decrease in most of the peaks intensities when compared to the lower irradiation gamma dose. This decrease affects the gamma quantum (1.2 MeV energy) and changes the lattice parameter values (of some atoms relate to their ideal position). The B_6Si samples gamma irradiated with adsorption dose $D \geq 145.5 \text{ kGy}$ also showed partial amorphization of the sample. To determine the amorphousness of silicide hexaboride the area in the XRD peak of unirradiated sample is divided by the XRD peak area of the irradiated samples. Fig. 2 showed amorphization of silicide hexaboride before and after gamma irradiation dose. About 54% of the sample was amorphized for the 145.5 kGy irradiated sample. Further decrease in the peak intensity and further

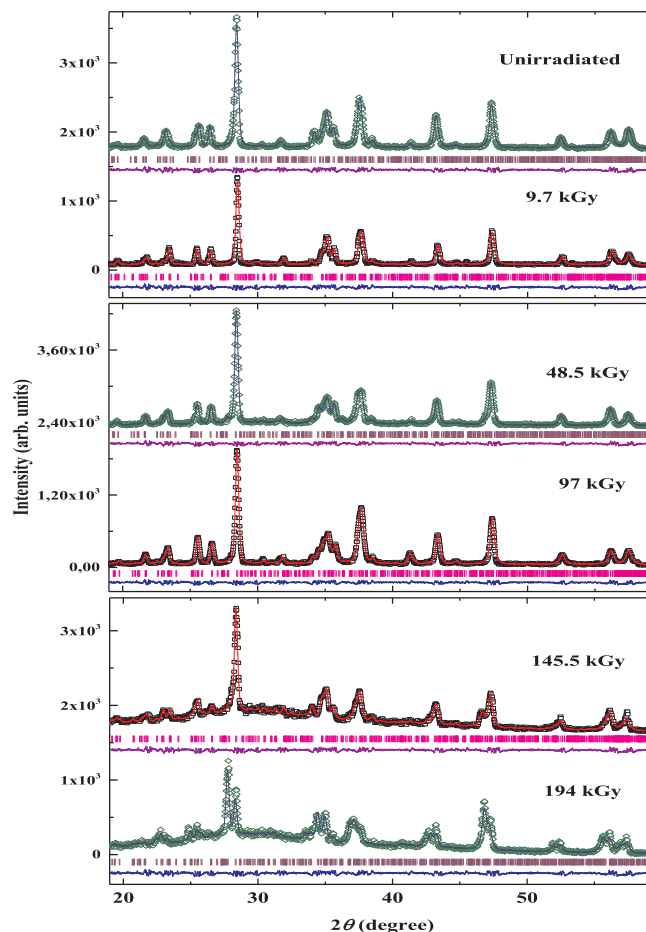


Fig. 1. XRD pattern for B_6Si before and after gamma irradiation with adsorption dose of 9.7 kGy, 48.5 kGy, 97 kGy, 145.5 kGy and 194 kGy.

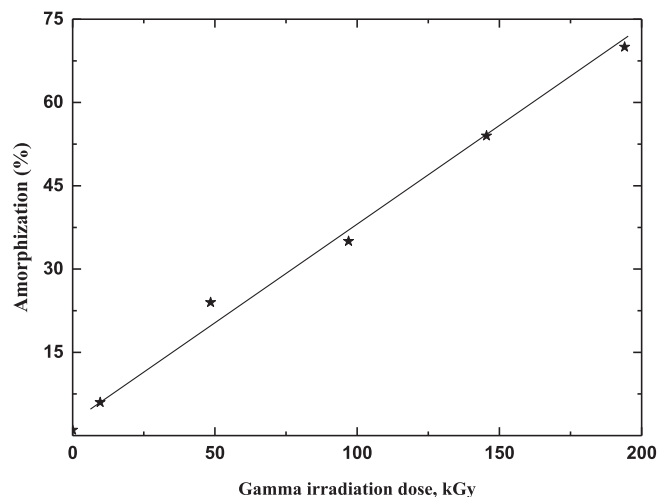


Fig. 2. Amorphization of silicide hexaboride with increase in gamma irradiation dose.

amorphization was observed for the samples irradiated with adsorption dose of $D = 194 \text{ kGy}$ and 69% for the 194 kGy sample. The lattice parameter and volume change of the elementary lattice of irradiated B_6Si is listed in Table 2. The result in Table 2 indicates that the lattice parameters increase with irradiation dose. The lattice parameter for a before irradiation was 14.060 \AA . After the sample was irradiation at 48.5 kGy and 194 kGy, the lattice parameter a changed to 14.096 \AA and 15.224 \AA respectively. Consequently, the volume of the samples

Table 2

Lattice parameters and lattice volume for B₆Si before and after gamma irradiation with different gamma irradiation dose at room temperature.

Gamma irradiation dose (kGy)	Lattice parameters and volume			
	a, Å	b, Å	c, Å	V, Å ³
0	14.060(6)	18.027(9)	9.269(2)	2349.(6)
9.7	14.072(2)	18.028(6)	9.269(7)	2351.(8)
48.5	14.096(5)	18.030(3)	9.271(3)	2356.(4)
97	14.156(9)	18.032(2)	9.274(2)	2367.(5)
145.5	14.190(2)	18.034(2)	9.276(5)	2373.(9)
194	14.224(7)	18.036(2)	9.278(4)	2380.(5)

increased with increase in irradiation dose, from 2349 Å³ before irradiation to 2356 Å³ and 2380 Å³ after irradiating at 48.5 kGy and 194 kGy respectively. The increase in the lattice volume and lattice parameters indicates the material is experiencing stress and strain. To determine the dependence of lattice parameters (a, b and c) on gamma adsorption dose of B₆Si, a graph of lattice parameter and adsorption dose was plotted and studied (see Fig. 3). The irradiation constant was calculated using Eq. (1) by taking the slope of the graph in Fig. 3.

$$k_i = \left(\frac{1}{a_{i0}} \right) \left(\frac{da_i}{dD} \right)_{p,T}$$

(where, k_i coefficient of expansion, a_{i0} lattice parameters of unirradiated sample, a_i lattice parameters of irradiated sample, D adsorption dose). The resulting k_i values (lining expanding the lattice parameters) were k_a = 6.2 × 10⁻⁵ kGy⁻¹, k_b = 2.3 × 10⁻⁶ kGy⁻¹, and k_c = 5.2 × 10⁻⁶ kGy⁻¹. As stated on the latter paragraph, increase in gamma irradiation results in increase in the lattice volume of B₆Si. Furthermore the lattice volume increased from V₀ = 2349.(6) Å³ to V_{194 kGy} = 2380.(5) Å³, which is equivalent to percentage lattice volume increase of 1.31%. Zhang et al. [25,23] reported on unirradiated B₆Si samples having different lattice structures in just a single sample. The effects of gamma irradiation in each lattice structure occurred in the condensation and phase passage. Because the intensity and energy of gamma irradiation change the location of atoms in the lattice and regularity is violated. At high adsorption dose, gamma irradiation created different point defects and active centres, which may migrate in the sample. The surface morphology and microstructural analysis of B₆Si before and after irradiation was investigated. The distribution of chemical elements on the surface of the sample was statistically characterized.

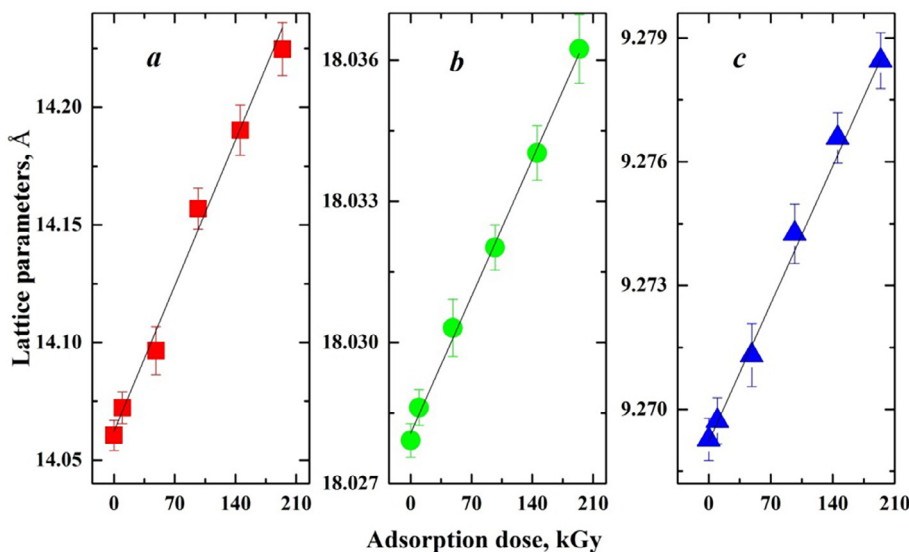


Fig. 3. Gamma irradiation dose dependences of lattice parameters of the orthorhombic phase of silicide hexaboride at room temperature. Solid lines are interpolation of the experimental data by linear functions polynomials.

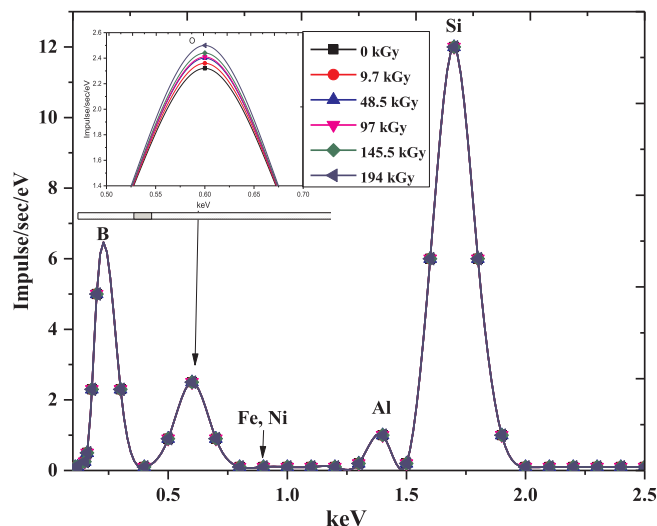


Fig. 4. Unirradiated and irradiated of sample distribution of chemical elements of silicide hexaboride.

Fig. 4. Showed the EDS results indicated the presence of B, Si, Al, Fe and Ni on the unirradiated and irradiated sample. The quantity of Ni, Al and Fe remained the same regardless of the change in irradiation dose. An increases in adsorption dose led to a parallel increases in the surface value. The oxygen atoms in active centres showed statistical growth of the oxidation process during the increase in adsorption dose. The temperature and weight axis was divided into two regions. The linear range T ≤ 470 K and T ≥ 470 K showed poor decrease range of weight kinetics. When the gamma adsorption dose was increased, a parallel decrease of weight kinetics was observed. Fig. 5 shows a shift in temperature to the high region and at maximum radiation, this difference is 25 K. This shows that, in high irradiation doses defects have high recombination rate and changes place to the high temperatures. The value representing the weight kinetics during the gamma irradiation is based on the following model. The first model: increase in adsorption dose causes an increase in temperature of the sample up to 420 K. As the sample cools down (cooling process), defects and active centres are created. The active centres on the surface are more active than the active centres deep in the material. OH group is chemisorbed on the

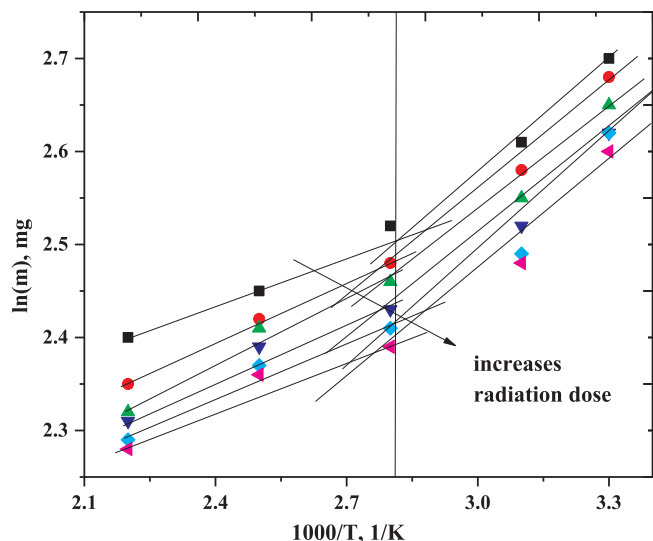


Fig. 5. Variation in the activation energy of silicide hexaboride sample with temperature from 300 K to 830 K. The organic binder was removed in an Ar atmosphere.

active centres. And with the influence of temperature degradation which OH groups of dipole interaction. It should be noted that these values were not measured during the gamma irradiation but post-irradiation measurement at room temperature were taken. This is because taking measurements during radiation is a very difficult process. Therefore, experiments are performed after irradiation. During radiation, the number of defects is slightly higher. Chemisorption and recombination is difficult to accurately analyse. Have been adsorption characterization of ceramics materials [6,7,15,16]. The second model is, “the defects concentration is dependent on the adsorption dose of gamma irradiation.” That is, increase in gamma irradiation adsorption dose leads to increase in defects concentration. Furthermore, depending on the temperature, defects recombination will have a different value. The two models play a major role in the processes observed in these results (created defects and recombination rate process). The activation energy calculated was seen to decrease with increase in gamma irradiation adsorption dose, see Table 3. as C/T^k (where $T(K)$ is the measurement temperature, C and k are the constants for each sample). For the unirradiated B_6Si , the parameter C is equal to 1, and it was reported that k decreases with the increase in gamma irradiation dose. Adsorption dose and activation energy for B_6Si sample are listed in Table 3. Activation energy was calculated from the Arrhenius approach in Fig. 3. To determine the values of activation energy during chemisorption and recombination processes [6,7]. At elevated temperatures point defects migrate in the solid. The diffusion of defects can be expressed as thermal activated jumps of atoms from their lattice site to another lattice sites. Silicide hexaboride samples which were gamma irradiated with different adsorption dose created two different energy levels (which are suitable). The first energy barrier changed from 0.14 eV at

Table 3
Gamma irradiation dose and activation energy for silicide hexaboride sample.

Sample	Gamma irradiation dose (kGy)	Activation energy (eV)	
		$T \leq 470$ K	$T \geq 470$ K
B_6Si	no irradiated	0.22	0.14
	9.7	0.41	0.21
	48.5	0.38	0.23
	97	0.38	0.21
	145.5	0.42	0.24
	194	0.46	0.26

0 kGy to 0.26 eV at 197 kGy and second energy barrier changed from 0.22 eV at kGy to 0.46 eV to 197 kGy at room temperature. The formation of the two energy levels in silicide hexaboride the location of the point defects in the deeper levels of energy and is located to the valence zone closer. Increase in irradiation (adsorption dose) led to increase in oxygen content present during the initial irradiation of the sample. The first time it was determined that silicide hexaboride compound $D \geq 145.5$ kGy irradiation dose has been amorphization.

Conclusions

The effect of irradiation of B_6Si and determining the energy state of the system before and after gamma irradiation was investigated. XRD and EDS were used to analyse the microstructural changes. A change in the lattice parameters was observed due to irradiation. The lattice volume of the B_6Si sample was observed to increase with increase in gamma irradiation dose. The increase in volume was attributed to the stress/stain experienced by the samples due to increase in gamma irradiation dose. A structural change from crystalline to amorphous state after irradiation was observed. Low irradiation dose (9.7 kGy, 48.5 kGy and 97 kGy) retained the crystalline structure while 145.7 kGy partial amorphization of the material was observed. Irradiating at 194 kGy led to an increase in amorphization on the B_6Si . At 145.5 kGy a processes of oxygen chemisorption was observed to increase by 1.5%. After gamma irradiated of the samples, two energy barrier states were created. The first energy barrier changed from 0.14 eV (0 kGy) to 0.26 eV a(197 kGy) and second energy barrier changes from 0.22 eV (0 kGy) to 0.46 eV (197 kGy) at room temperature.

Appendix A. Supplementary data

Supplementary data associated with this article can be found, in the online version, at <https://doi.org/10.1016/j.rinp.2018.06.034>.

References

- [1] Aghajanian MK, Morgan BN, Singh JR, Mears J, Wolfee RA. A new family of reaction bonded ceramics for armor applications. *Ceram Trans* 2002;134:527–39.
- [2] Armas B, Male G, Salanljbat D, Chaitillon C, Allibert M. Determination of the boron-rich side of the B-Si phase diagram. *J Less-Common Metals* 1981;82:245–54.
- [3] Chen HM, Qi HY, Zheng F, Liu LB, Jin ZP. Thermodynamic assessment of the B-C-Si system. *J Alloy Compd* 2009;481:182–9.
- [4] Flynn JH. A general differential technique for the determination of parameters for $d(\alpha)/dt = f(\alpha)A \exp(-E/RT)$. Energy of activation, preexponential factor and order of reaction (when applicable). *J Ther Anal* 1991;3:125–9.
- [5] Flynn JH. Thermal analysis kinetics-problems, pitfalls and how to deal with them. *J Ther Anal* 1988;34:367–73.
- [6] Garibov AA, Agaev TN, Mirzoev MN, Aliev SM. Heterogeneous water radiolysis in the presence of uranyl silicate. *Prot Met Phys Chem* 2015;51:527–32.
- [7] Garibov AA, Agaev TN, Mirzoev MN, Aliev SM. Water radiolysis in the presence of uranyl silicate. *Russ J Phys Chem A* 2015;89:1939–43.
- [8] Jerome R, Volodymyr B, Jean-Francois H, Roland G. Boron-silicon solid solution: synthesis and crystal structure of a carbon-doped boron-rich $SiBn$ ($n \sim 30$) compound. *J Solid State Chem* 2004;177:4167–74.
- [9] Jijun W, Wenhui M, Duzuo T, Binjie J, Bin Y, Dachun L, Yongnian D. Thermodynamic description of Si-B binary system. *Procedia Eng* 2012;31:297–301.
- [10] Khattak CP, Joyce DB, Schmid F. A simple process to remove boron from metallurgical grade silicon. *Sol Energy Mater Sol Cells* 2002;74:77–89.
- [11] Liu YS, Zhang LT, Cheng LF. Preparation and oxidation protection of CVD SiC/a-BC/SiC coatings for 3D C/SiC composites. *Corros Sci* 2009;51:820–6.
- [12] Mallick D, Kayal TK, Ghosh J, Chakrabarti OP, Biswas S, Maiti HS. Development of multi-phase B-Si-C ceramic composite by reaction sintering. *Ceram Int* 2009;35:1667–9.
- [13] Matsushita J, Komarinen S. High temperature oxidation of silicon hexaboride ceramics. *Mater Res Bull* 2001;36:1083–9.
- [14] Murakami T, Inui H. Friction and wear properties of α - AlB_{12} - and SiB_6 -based ceramics in water. *Tribol Int* 2014;74:38–45.
- [15] Mirzayev MN, Mehdiyeva RN, Garibov RG, Ismayilova NA, Jabarov SH. Influence of gamma irradiation on the surface morphology, XRD and thermophysical properties of silicide hexaboride. *Mod Phys Lett B* 2018;32:1850151.
- [16] Mirzayev MN, Mammadov KhF, Garibov RG, Askerov EB. Studying of thermophysical properties of the boron carbide irradiated by ionizing radiation. *High Temp* 2018;56:374–7.
- [17] Shi FM, Yin XW, Fan XM. A new route to fabricate SiB_4 modified C/SiC composites. *J Eur Ceram Soc* 2010;30:1955–62.

- [18] Tea KK, Jaeyun M, Bryan VS, Dongwon Ch, Calvin JG, Jae-Young J, Gang W, Renkun Ch, Zhaowei L, Yu Q, Sungho J. Si boride-coated Si nanoparticles with improved thermal oxidation resistance. *Nano Energy* 2014;9:32–40.
- [19] Tong CQ, Cheng LF, Yin XW, Zhang LT, Xu YD. Oxidation behavior of 2D C/SiC composite modified by SiB₄ particles in inter-bundle pores. *Compos Sci Technol* 2008;68:602–7.
- [20] Vlasse M, Slack GA, Garbaskas M, Kasper JS, Viala JC. The crystal structure of SiB₆. *J Solid State Chem* 1986;63:31–45.
- [21] Wu JJ, Mu WH, Yang B, Dai YN, Morita K. Boron removal from metallurgical grade silicon by oxidizing refining. *Trans Nonferrous Met Soc China* 2009;19:463–7.
- [22] Xiaoyu C, Xiaowei Y, Xiaokang M, Xiaomeng F, Laifei Ch, Litong Zh. Oxidation behavior of SiBC matrix modified C/SiC composites with different PyC interphase thicknesses. *Ceram Int* 2015;41:1695–700.
- [23] Yanchao W, Jian L, Zhu L, Yanming M. Crystal structure prediction via particle-swarm optimization. *Phys Rev B* 2010;82:094116.
- [24] Zaitsev AI, Kodentsov AA. Thermodynamic properties and phase equilibria in the Si-B system. *J Phase Equilib* 2001;22:126–35.
- [25] Zhang B, Lailei W, Zhihong L. Predicted structural evolution and detailed insight into configuration correlation, mechanical properties of silicon–boron binary compounds. *RSC Adv* 2017;26:16109–18.
- [26] Zsako J, Zsako Jr. J. Kinetic analysis of thermogravimetric data. XIV. Three integral methods and their computer programs. *J Therm Anal* 1980;19:333–59.